

NEW YORK STATE
DEPARTMENT OF TRANSPORTATION
MATERIALS BUREAU
JOB MIX FORMULA

Facility No. _____ Formula No. _____
Plant Willets Point Asphalt Region 11
Plant Location Flushing, NY
Submitted Willets Point Asphalt Date 9/1/2011

J. Santora QC Supervisor


NYSDOT TYPE 6FHD/RA TOP COURSE (HIGH FRICTION)

WilletsPointAsphalt/Generic/6FRA/AspTop/NYCDDC/010/11

Expires on 10/31/13

AGGREGATE SAMPLING FREQUENCY

SAMPLE _____

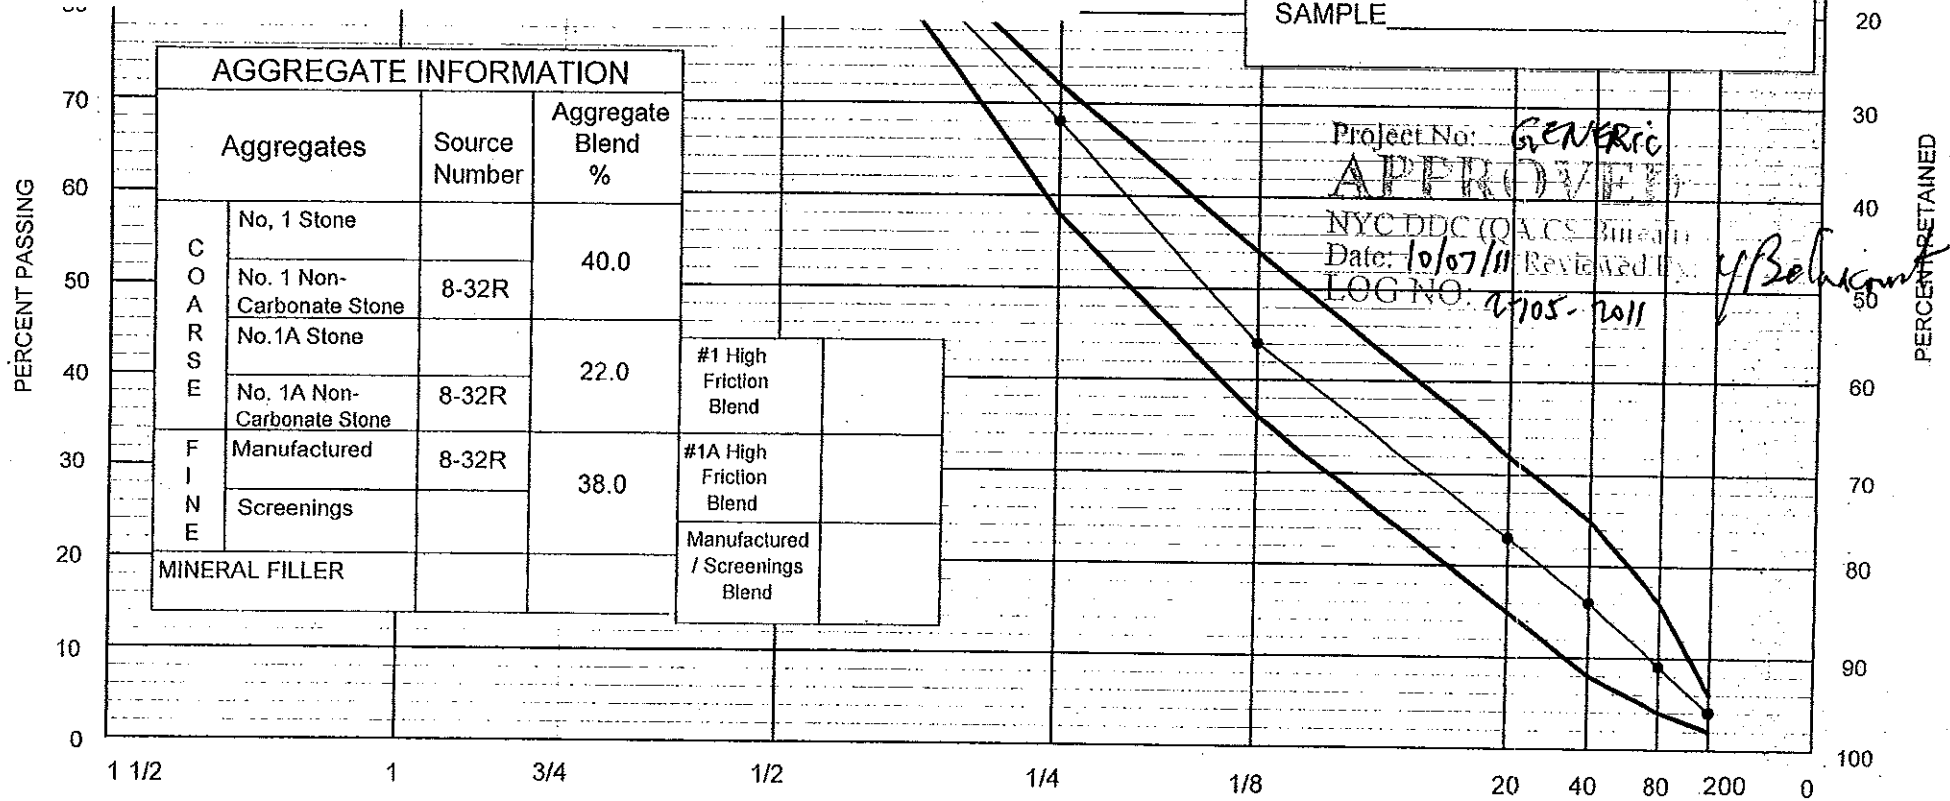

U.S. STD. - SIZES RAISED TO 0.45 POWER

Sieve Size	1 1/2"	1"	3/4"	1/2"	1/4"	1/8"	No. 20	No. 40	No. 80	No. 200	Asphalt Content (Percent)
% Passing	1. Generi Limits										
	2. JMF Range										
	3. Target Value										
			100	95-100	58-72	36-54	15-32	8-25	4-16	2-6	5.0-6.2
			100	95-100	63-73	40-48	19-27	12-20	6-12	2-6	-
			100	99	68	44	23	16	9	4	5.5

Asphalt Grade
AC 20 PG 64-22

Recommended for Approval by Regional Director _____

Date: _____

Approved by Director, Materials Bureau _____

Date: _____

Remarks: _____