


NEW YORK STATE  
DEPARTMENT OF TRANSPORTATION  
MATERIALS BUREAU  
JOB MIX FORMULA

Facility No. \_\_\_\_\_ Formula No. \_\_\_\_\_  
Plant Willets Point Asphalt Region 11  
Plant Location Flushing, NY  
Submitted Willets Point Asphalt Date 9/1/11

*J. Santora* QC Supervisor

NYSDOT TYPE 3 HD/RA BINDER

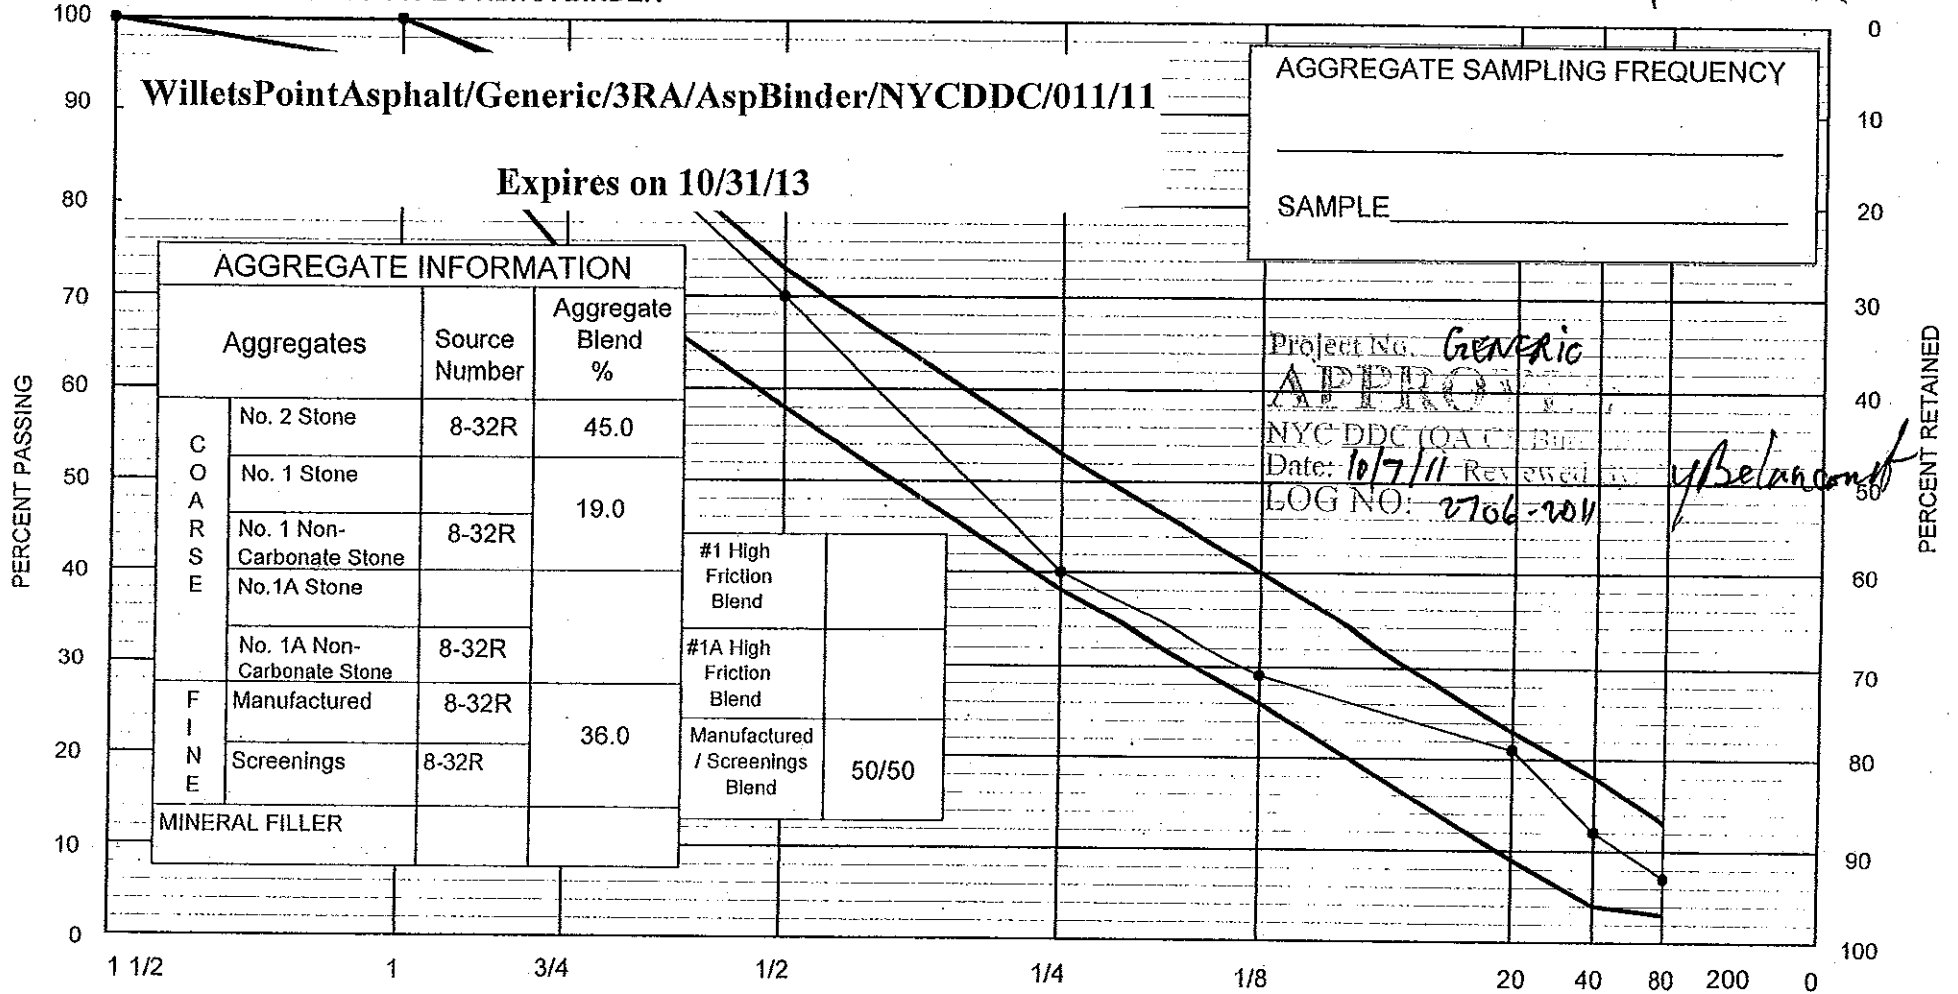

Sieve Size	1 1/2"	1"	3/4"	1/2"	1/4"	1/8"	No. 20	No. 40	No. 80	No. 200	Asphalt Content (Percent)
% Passing	100	95-100	74-93	58-73	38-53	26-40	9-23	4-18	3-13	2-6	4.0-6.0
1. Genert Limits	100	95-100	74-93	58-73	38-53	26-40	9-23	4-18	3-13	2-6	4.0-6.0
2. JMF Range	100	95-100	87-97	65-75	35-45	24-34	17-25	8-16	4-10	1-5	-
3. Target Value	100	100	92	70	40	29	21	12	7	3	4.5

Asphalt Grade
AC 20
PG 64-22

Recommended for Approval by Regional Director \_\_\_\_\_

Date: \_\_\_\_\_

Approved by Director, Materials Bureau \_\_\_\_\_

Date: \_\_\_\_\_

Remarks: \_\_\_\_\_